



HAL
open science

Dynamic Recrystallization Behaviours in Metals and Alloys

Frank Montheillet

► **To cite this version:**

Frank Montheillet. Dynamic Recrystallization Behaviours in Metals and Alloys. *Materials*, 2023, 16 (3), pp.976. 10.3390/ma16030976 . emse-04197581

HAL Id: emse-04197581

<https://hal-emse.ccsd.cnrs.fr/emse-04197581>

Submitted on 6 Sep 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution| 4.0 International License

Dynamic Recrystallization Behaviours in Metals and Alloys

Frank Montheillet 

CNRS, UMR 5307 Laboratoire Georges Friedel, Centre SMS, Mines Saint-Etienne, 158 cours Fauriel, CEDEX 2, 42023 Saint-Etienne, France; montheil@emse.fr

The existence of dynamic recrystallization (DRX), i.e., recrystallization occurring during straining, has long been questioned [1] despite the publication of strong mechanical and microstructural evidence [2]. Some authors later showed that it was not merely a “laboratory curiosity” but in fact a real “industrial tool” [3]. Currently, DRX has been definitively recognized as the most important physical mechanism associated with the hot working of metals and alloys, an understanding of which is key to the optimization of microstructural and mechanical properties.

Although DRX was first imagined to take place exclusively in low to medium stacking fault energy (SFE) materials, it was later observed that high SFE metals, such as ferritic steels or aluminium alloys, also exhibit recrystallization-like microstructure transformations during hot working. In the first case, DRX occurs by nucleation and the growth of new grains, which has been termed discontinuous DRX (DDRX); in the second case, DRX results from the progressive “fragmentation” of the initial grains and is often referred to as continuous DRX (CDRX) [4]. The aim of this Special Issue is to present recent novel research on this wide topic. The behaviour of a variety of alloys submitted to new hot-working processes (Figure 1) and/or with new compositions is addressed, which highlights the importance of DRX in the whole field of the thermomechanical processing of metals (Figure 2).



Citation: Montheillet, F. Dynamic Recrystallization Behaviours in Metals and Alloys. *Materials* **2023**, *16*, 976. <https://doi.org/10.3390/ma16030976>

Received: 11 January 2023
Accepted: 13 January 2023
Published: 20 January 2023



Copyright: © 2023 by the author. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

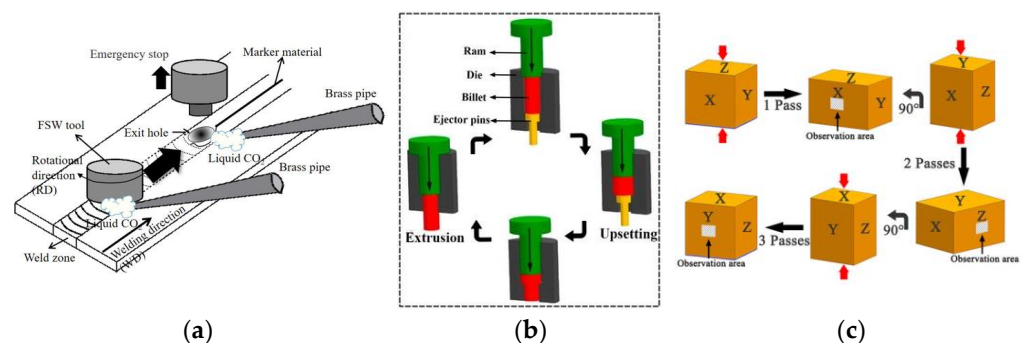


Figure 1. Schematic representations of some processes used to prescribe large-strain hot deformations: (a) friction stir welding [5]; (b) reciprocating upsetting-extrusion [6]; (c) multidirectional forging [7].

Nagira et al.’s paper [5] investigates the DRX of both commercial-grade and high-purity aluminium occurring during friction stir welding; possible transitions between DDRX and CDRX are revealed, which are associated with distinct texture components. Dolzhenko et al.’s article [8] deals with DRX in an austenitic stainless steel containing about 10 vol% ferrite together with a small fraction of nanometric Z-phase (CrNbN) particles submitted to compression tests. Power-law functions are used to relate the various mechanical and microstructural parameters to each other.

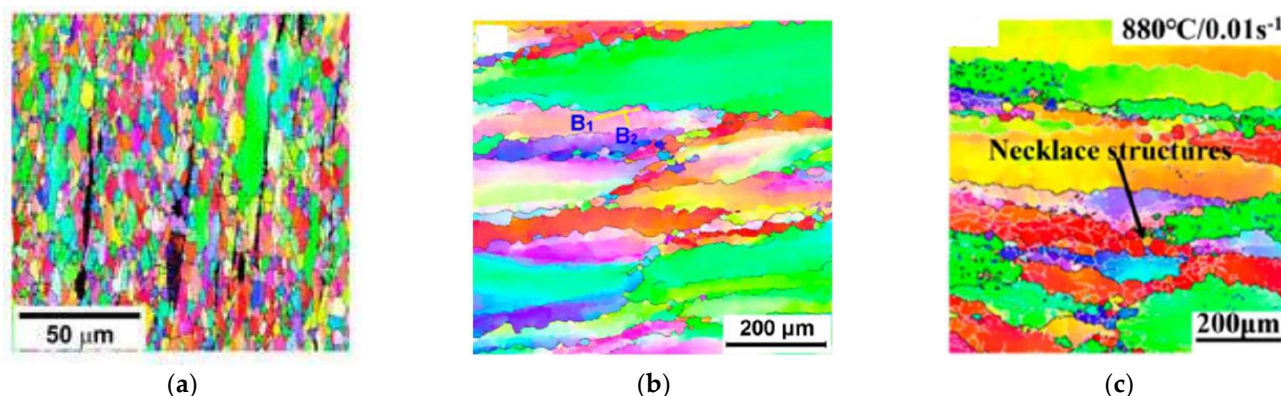


Figure 2. Examples of microstructures exhibiting DRX in various alloys: (a) DDRX in a highly alloyed austenitic stainless steel (1000 °C, 10^{-4} s^{-1} , $\varepsilon = 1$) [8]; (b) onset of CDRX/DDRX in a Zr-Ti-Al-V alloy (800 °C, 10^{-2} s^{-1} , $\varepsilon = 0.7$) [9]; (c) onset of CDRX in Ti-35421 (880 °C, 10^{-2} s^{-1} , $\varepsilon = 0.9$) [10].

Two contributions are devoted to near- β titanium alloys deformed in uniaxial compression in both the α and $\alpha + \beta$ domains: Zhou et al. [10] investigate a low-cost iron-containing alloy, while Buzolin et al. [11] develop mesoscale models to predict the flow stress and microstructure evolutions of the Ti-5553 and Ti-17 grades. Microstructure and texture evolutions of a new Zr-Ti-Al-V alloy are investigated by Lei et al. [9], who point out the co-existence of DDRX and CDRX.

Three papers deal with the hot working of magnesium alloys, which are much less frequently mentioned in the literature. Two similar Mg-Gd-Y alloys are submitted to large strains by Wu et al. [6] and Liu et al. [7] using reciprocating upsetting-extrusion and multi-directional forging deformation processes, respectively. In a similar way, Ullmann et al. [12] investigate a twin-roll-cast Mg-Y-Zn alloy by plane-strain compression. The articles converge on the conclusion that complex CDRX and/or DDRX mechanisms lead to grain refinement and texture weakening, thus improving formability.

Finally, a theoretical paper by Montheillet [13] points out the importance of the softening induced by grain boundary migration (BMIS) during DDRX, in particular for the estimation of grain boundary mobility from experimental data.

Conflicts of Interest: The author declares no conflict of interest.

References

1. Stüwe, H.P. Do metals recrystallize during hot working? In *Deformation under Hot Working Conditions*; Tegart, W.J.M., Sellars, C.M., Eds.; ISI Special Report 108; Iron and Steel Institute: London, UK, 1968; pp. 1–6.
2. Thomsen, E.G.; Yang, C.T.; Bierbower, J.B. *An Experimental Investigation of the Mechanics of Plastic Deformation of Metals*; University of California Press: Berkeley, CA, USA, 1954.
3. Jonas, J.J. Dynamic recrystallization—Scientific curiosity or industrial tool? *Mater. Sci. Eng. A* **1994**, *184*, 155–165. [[CrossRef](#)]
4. Huang, K.; Logé, R.E. A review of dynamic recrystallization phenomena in metallic materials. *Mater. Design* **2016**, *111*, 548–574. [[CrossRef](#)]
5. Nagira, T.; Liu, X.; Ushioda, K.; Fujii, H. Microstructural evolutions of 2N grade pure Al and 4N grade highpurity Al during friction stir welding. *Materials* **2021**, *14*, 3606. [[CrossRef](#)] [[PubMed](#)]
6. Wu, G.; Yu, J.; Jia, L.; Xu, W.; Dong, B.; Zhang, Z.; Hao, B. Microstructure and texture evolution of Mg-Gd-Y-Zr alloy during reciprocating upsetting-extrusion. *Materials* **2020**, *13*, 4932. [[CrossRef](#)] [[PubMed](#)]
7. Liu, H.; Meng, Y.; Yu, H.; Xu, W.; Zhang, S.; Jia, L.; Wu, G. The role of long period stacking ordered phase in dynamic recrystallization of a Mg-Gd-Y-Zn-Zr alloy during multi-directional forging process. *Materials* **2020**, *13*, 3290. [[CrossRef](#)] [[PubMed](#)]
8. Dolzhenko, P.; Tikhonova, M.; Kaibyshev, R.; Belyakov, A. Peculiarities of DRX in highly-alloyed austenitic stainless steel. *Materials* **2021**, *14*, 4004. [[CrossRef](#)] [[PubMed](#)]
9. Lei, Y.; Yang, Y.; Tan, Y.; Zhang, W.; Wu, S.; Ma, M. Effect of hot working parameters on microstructure and texture evolution of hot-deformed Zr-45Ti-5Al-3V alloy. *Materials* **2022**, *15*, 1382. [[CrossRef](#)] [[PubMed](#)]
10. Zhou, D.; Gao, H.; Guo, Y.; Wang, Y.; Dong, Y.; Dan, Z.; Chang, H. High temperature deformation behavior and microstructural characterization of Ti-35421 titanium alloy. *Materials* **2020**, *13*, 3623. [[CrossRef](#)] [[PubMed](#)]

11. Buzolin, R.H.; Miller Branco Ferraz, F.; Lasnik, M.; Krumphals, A.; Poletti, M.C. Improved predictability of microstructure evolution during hot deformation of titanium alloys. *Materials* **2020**, *13*, 5678. [[CrossRef](#)] [[PubMed](#)]
12. Ullmann, M.; Kittner, K.; Prah, U. Hot deformation and dynamic recrystallization behavior of twin-roll cast Mg-6.8Y-2.5Zn-0.4Zr magnesium alloy. *Materials* **2021**, *14*, 307. [[CrossRef](#)] [[PubMed](#)]
13. Montheillet, F. Influence of boundary migration softening on the steady state of discontinuous dynamic recrystallization. *Materials* **2021**, *14*, 3531. [[CrossRef](#)] [[PubMed](#)]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.